

RZ 3245 (# 93291) 06/19/00  
Computer Science/Mathematics 17 pages

# Research Report

## Electron mobility in Alq<sub>3</sub> determined via transient electroluminescence from single- and multilayer organic light-emitting diodes

S. Barth, P. Müller, H. Riel, P.F. Seidler, W. Rieß

IBM Research  
Zurich Research Laboratory  
8803 Rüschlikon  
Switzerland

H. Vestweber

Covion Organic Semiconductors GmbH  
Industrial Park Höchst  
Building G 864  
D-65926 Frankfurt am Main  
Germany

H. Bässler

Institute of Physical-, Nuclear- & Macromolecular Chem.  
& Center of Material Science  
Philipps-University of Marburg  
Hans-Meerwein-Strasse  
D-35032 Marburg  
Germany

### LIMITED DISTRIBUTION NOTICE

This report has been submitted for publication outside of IBM and will probably be copyrighted if accepted for publication. It has been issued as a Research Report for early dissemination of its contents. In view of the transfer of copyright to the outside publisher, its distribution outside of IBM prior to publication should be limited to peer communications and specific requests. After outside publication, requests should be filled only by reprints or legally obtained copies of the article (e.g., payment of royalties).

# Electron mobility in Alq<sub>3</sub> determined via transient electroluminescence from single- and multilayer organic light-emitting diodes

S. Barth, P. Müller, H. Riel, P.F. Seidler, W. Rieß

*IBM Research, Zurich Research Laboratory, 8803 Rüschlikon, Switzerland*

H. Vestweber

*Covion Organic Semiconductors GmbH, Industrial Park Höchst, Building G 864, D-65926 Frankfurt am Main, Germany*

H. Bässler

*Institute of Physical-, Nuclear- & Macromolecular Chem. & Center of Material Science, Philipps-University of Marburg, Hans-Meerwein-Strasse, D-35032 Marburg, Germany*

## Abstract

Transient electroluminescence (EL) from single- and multilayer organic light-emitting diodes (OLEDs) was investigated by driving the devices with short, rectangular voltage pulses. The single-layer devices consist of indium-tin oxide (ITO) / tris(8-hydroxy-quinoline)aluminum (Alq<sub>3</sub>) / magnesium (Mg): silver (Ag), whereas the structure of the multilayer OLEDs are ITO / copper phthalocyanine (CuPc) / N,N'-di(naphthalene-1-yl)-N,N'-diphenyl-benzidine (NPB) / Alq<sub>3</sub> / Mg:Ag. Apparent model-dependent values of the electron mobility ( $\mu_e$ ) in Alq<sub>3</sub> have been calculated from the onset of EL for both device structures upon invoking different internal electric field distributions. For the single-layer OLEDs, transient experiments with different dc bias voltages indicated that the EL delay time is determined by the accumulation of charge carriers inside the device rather than by transport of the latter. This interpretation is supported by the observation of delayed EL after the voltage pulse is turned off. In the multilayer OLED the EL onset—dependent on the electric field—is governed by accumulated charges (holes) at the internal organic-organic interface (NPB/Alq<sub>3</sub>) or is transport-limited. Time-of-flight (TOF) measurements on 150-nm-thin Alq<sub>3</sub> layers yield weak field-dependent  $\mu_e$  values of the order of  $1 \times 10^{-5}$  cm<sup>2</sup>/Vs at electrical fields between  $3.9 \times 10^5$  and  $1.3 \times 10^6$  V/cm.

# 1 Introduction

Since the first observation of efficient bright emission from a triphenylamine derivative / Alq<sub>3</sub> double layer structure [1], organic light-emitting diodes (OLEDs) have been studied extensively due to their potential application in flat-panel displays [2, 3, 4, 5, 6, 7, 8, 9]. Besides efficiency, long-term stability, peak brightness and stability under high driving conditions, the response time of OLEDs is an essential criterion for their application in such thin-film displays. The response time, i.e. the time lag between addressing the device by a short, rectangular voltage pulse and the first appearance of electroluminescence (EL), is determined by the superposition of various elementary electronic processes: charge-carrier injection, charge-carrier transport, buildup of space charges, formation of the excited state, and the radiative decay of the excited state. It is usually difficult to disentangle these electronic processes. One way to do so involves time-resolved studies, e.g. transient EL measurements. Meanwhile time-resolved EL experiments have been successfully applied to organic crystals [10, 11], low-molar-mass organic compounds [12, 13, 14, 15, 16, 17, 18, 19, 20, 21, 22, 23], and polymeric materials [24, 25, 26, 27, 28, 29, 30, 31, 32, 33, 34, 35, 36, 37, 38, 39, 40, 41, 42, 43, 44, 45]. However, the interpretation of the results often turns out to be difficult. In a single-layer OLED the time-dependent EL onset, also called the delay time  $t_d$ , is identified as the time until the two leading fronts of injected carriers—holes and electrons—meet in the device. The time after the EL tends to saturate (rise time  $t_r$ ) is the time till electron and hole distribution have interpenetrated, which is controlled by the charge-carrier motion into the bulk of the sample. In a double or multilayer structure the situation is even more complicated because of possible charge-carrier accumulation at the internal interface or interfaces, respectively. In bilayer structures, for example,  $t_d$  is the time until the leading front of minority carriers—in most cases electrons—reach the internal organic–organic interface and recombine with the first injected opposite charge carriers waiting at that interface, whereas  $t_r$  reflects the buildup of the minority carrier density in the recombination zone. The temporal decay pattern of the EL at the end of the applied voltage pulse reflects the depletion of the charge-carrier reservoir established during the preceding on-phase. The corresponding EL signal differs in a characteristic way for single and bi- or multilayer devices. Whereas in the former the EL decays monotonously, the latter structures often feature an EL overshoot following the end of the voltage pulse [46].

It is common practice that in single-layer devices the onset of EL is interpreted as being the transit time ( $t_{tr}$ ) of the majority charge carriers. However, it has been found that the mobility values obtained via  $t_d$ , from single- as well as double-layer systems, are orders of magnitude lower than those determined from time-of-flight (TOF) measurements, especially at low voltages [15, 28, 30]. This discrepancy was attributed to the accumulation of space charges at interfacial barriers, which have a major effect on  $t_d$  in time-resolved EL experiments. This interpretation was recently confirmed for a double-layer device by an analytical theory [47]. It has been shown that the EL onset is governed by the growth of the interfacial charge densities and the concomitant redistribution of the electric field inside the sample rather than by charge-carrier transport. Therefore it is all but straightforward to identify  $t_d$  with  $t_{tr}$ . However, transient EL measurements have the advantage that they provide information directly from the emitting device. So far there exists no detailed TOF investigations under operation conditions of OLEDs, i.e. in devices with a typical thickness of 100 nm and under the action of electric fields exceeding 10<sup>6</sup> V/cm, to determine the charge-carrier mobilities in such thin films.

In this work we report on transient EL measurements of multilayer OLEDs, which con-

sist of indium-tin oxide (ITO) / copper phthalocyanine (CuPc) / N,N'-di(naphthalene-1-yl)-N,N'-diphenyl-benzidine (NPB) / tris(8-hydroxy-quinoline) aluminum (Alq<sub>3</sub>) / magnesium (Mg):silver (Ag). In order to investigate the mechanism of the time evolution of the EL in single-layer devices, we performed experiments on an ITO / Alq<sub>3</sub> / Mg:Ag OLED. Transient experiments with different dc bias voltages and investigations of the EL decay behavior were performed to clarify the influence of space charges on the EL onset. In addition we present TOF measurements on a 150-nm-thin Alq<sub>3</sub> film to determine the electron mobility in Alq<sub>3</sub> under operation conditions of OLEDs and to compare these results with mobility values calculated from time-resolved EL experiments.

## 2 Experimental

Our single-layer OLEDs consist of glass substrates (7059 Corning) covered with a patterned ITO anode (surface resistance 45 Ω / square, 80 nm thickness), followed by a 100-nm-thin Alq<sub>3</sub> layer as active material and finally a Mg:Ag (10:1) alloy as metal top cathode. The structure of the multilayer OLEDs is ITO as anode, CuPc as buffer layer, NPB as hole transport layer, Alq<sub>3</sub> as electron transport and emitting layer, and a Mg:Ag (10:1) alloy as cathode. The devices for the TOF measurements consist of ITO, Alq<sub>3</sub> as charge-transport layer (CTL), 5, 6, 11, 12-tetraphenyl-naphthacene (rubrene) as charge-generation layer (CGL), and Mg:Ag (10:1) as counterelectrode. The schematic device structures together with the energy-level diagrams and the molecular structures of the materials used are shown in Figs. 1(a-c).

All layers were prepared in a high-vacuum system (Leybold) by vapor deposition using resistively heated tantalum and tungsten boats. The base pressure in the chamber ranged between  $4 \times 10^{-7}$  and  $2 \times 10^{-6}$  mbar. The typical deposition rate for the organic materials and the metals was about 1 Å/s. For the deposition of the Mg:Ag alloy the evaporation rates of Mg and Ag were controlled independently by separate thin-film deposition monitors (Leybold Infikon). The active area of our devices was  $2 \times 2$  mm<sup>2</sup>. The evaporation chamber was attached directly to a glovebox, which allows device fabrication, first characterizations, encapsulation, and storage of the devices completely under inert (argon) conditions.

For the transient EL experiments we used a HP 8116A DC pulse/function generator (50 MHz, rise time  $\cong 7$  ns, decay time  $\cong 10$  ns) to apply rectangular voltage pulses to our devices. The repetition rate of the pulses was 1 kHz, the pulse length varied between 5 and 10 μs. In addition the function generator permits us to drive the OLEDs with various offset voltages before applying the rectangular voltage pulses. The encapsulated devices were fixed in a rebuilt HP 16058A test fixture together with a Hamamatsu photomultiplier 5783-01 (time resolution  $\cong 0.65$  ns) located directly on top of the emitting area to detect the EL intensity. The photomultiplier was connected to the 50 Ω input resistance of a digital oscilloscope (Tektronix 2440, sampling rate: 500 MS/s, resolution: 200 mV) to record the time-dependent EL signals. Our experimental setup allows us to detect with a second digital oscilloscope (Tektronix 2440) the applied voltage pulse and the time-dependent cell current through the devices simultaneously with the EL signal. Both oscilloscopes were connected to a personal computer for the transfer and evaluation of the experimental data. The RC time constant of our setup, including the OLED device, was  $\cong 0.2$  μs.

The transient photocurrents were recorded with the TOF technique [48]. The charge carriers were generated in a 10-nm-thin rubrene layer, which served as CGL, by illumination through the ITO anode with pulses of a Nd:YAG pumped optical parametric oscillator (OPO) (Spectra

Physics GCR 170 and MOPO 710) driven at 530 nm (pulse duration = 8 ns, repetition rate = 10 Hz). The photocurrents were amplified by a low noise current amplifier (HVA, FEMTO Messtechnik) and recorded by a digital oscilloscope (Tektronix TDS 640 A, 500 MHz, sampling rate: 2 GS/s). To avoid space-charge accumulation in the device the excitation density was chosen to limit the emitted charge to  $0.05 CU$ , where  $C$  is the device capacitance and  $U$  the applied voltage. After each measurement the sample was shorted and kept in the dark for a few minutes before the next signal was taken. During the measurements the device was held in a cryostat under vacuum ( $\cong 10^{-5}$  mbar). All experiments—transient EL and TOF—were performed at room temperature.

### 3 Results

Figure 2 presents the transient behavior of the EL of an ITO / CuPc (20 nm) / NPB (45 nm) / Alq<sub>3</sub> (50 nm) / Mg:Ag multilayer OLED upon applying a rectangular voltage pulse of 16 V. The pulse length was 5  $\mu$ s, the repetition rate 1 kHz and the EL signal was averaged over 256 samples. The EL onset occurs with a delay time of  $\cong 0.48 \mu$ s. For  $t > t_d$  the EL signal increases and tends to saturate after  $\cong 1.76 \mu$ s, defined by the intercept of the tangents. For comparison the cell current is also plotted in Fig. 2. The voltage dependence of the transient EL of the multilayer structure is shown Fig. 3. With increasing voltage a decreasing delay time and a steeper rise of the EL is observed. At the beginning and end of the applied voltage pulses, weak parasitic effects—negative and positive peaks—occur in the EL signal (Figs. 2 and 3), which are caused by capacitive coupling effects. In Fig. 4(a) a typical function generator output signal of 10  $\mu$ s pulse width is presented. The corresponding EL signal together with the cell current of an ITO / Alq<sub>3</sub> (100 nm) / Mg:Ag single-layer OLED is shown in Fig. 4(b) detected under the same experimental conditions as for the multilayer device in Fig. 2. The EL grows after  $\cong 0.64 \mu$ s and  $t_r$  is determined to be  $\cong 2.32 \mu$ s. Figure 5 presents the time-resolved EL of the single-layer structure parametric in the applied voltage. With increasing voltage a decreasing EL onset and a steeper rise of the EL is observed, equivalent to a faster response time of the OLED. It is noteworthy to point out that  $t_d$  and  $t_r$  exceed the values measured with the multilayer device. The transient EL behavior of the single-layer OLED upon applying different positive and negative offset voltages before the rectangular voltage pulse is shown in Fig. 6. The pulse length was 10  $\mu$ s and the repetition rate 1 kHz. Both  $t_d$  and  $t_r$  are influenced by different dc bias voltages. With increasing negative offset voltages  $t_d$  and  $t_r$  increase, whereas increasing positive offset voltages lead to decreasing  $t_d$  and  $t_r$ . The inset depicts an enlargement of the EL decay behavior for the various offset voltages. Figure 7 presents a detailed investigation of the EL decay of an ITO / Alq<sub>3</sub> (100 nm) / Mg:Ag sample after the voltage pulse has been turned off. The EL decay signal is nonexponential and can be represented by two exponential decays with time constants of  $\cong 0.3 \mu$ s and  $\cong 10 \mu$ s, respectively. Figure 8 shows a typical TOF signal of an ITO / Alq<sub>3</sub> (150 nm) / rubrene (10 nm) / Mg:Ag device obtained at an electric field of  $5.9 \times 10^5$  V/cm. In Fig. 8(a) the dispersive current transient is plotted in a double linear representation and in Fig. 8(b) on a double logarithmic scale. In the latter figure  $t_{tr}$  is determined from the intersection of the asymptotes to the current transient to be  $\cong 1.1 \mu$ s. In addition the time required for the current to decrease to one-half of its value at  $t_{tr}$  is shown ( $t_{1/2} \cong 2.4 \mu$ s).

## 4 Discussion

First we shall discuss the time-resolved behavior of the EL of an ITO / CuPc (20 nm) / NPB (45 nm) / Alq<sub>3</sub> (50 nm) / Mg:Ag multilayer OLED. The energy-level diagram under flat band conditions [49, 50] portrayed in Fig. 1(b) clearly proves the existence of energy barriers for both electrons and holes at the NPB / Alq<sub>3</sub> interface. Therefore the observed green emission [51] from the device (peak maximum at about 515 nm, color coordinates 0.30, 0.52) can be attributed to the recombination of accumulated holes and electrons at this interfacial layer. It is also straightforward to associate the transient EL behavior with this interfacial charging. However, one has to clarify whether the buildup of space charges at the NPB/Alq<sub>3</sub> interface determine the EL onset in the entire electric field range investigated or merely modify  $t_d$  in a part of this range where, for example, the charge-carrier transport can predominate.

In Fig. 9 it is shown that for applied rectangular voltage pulses  $\leq 9$  V the calculated electron mobilities ( $\mu_e$ ) are field dependent, whereas for  $\geq 10$  V,  $\mu_e$  is field independent, irrespective of how the data was calculated (see below). The latter indicates that at higher electrical fields  $t_d$  is limited by the charge-carrier transport and at lower fields by space-charges due to accumulated holes and electrons at the NPB/Alq<sub>3</sub> interface. A detailed analysis of  $t_d$  (for low electric fields) as a function of the cell current  $j$  yields an inverse relationship between  $t_d$  and  $j$ , i.e.  $t_d$  decreases with increasing  $j$ . In addition the product  $j t_d$  being of the same order of magnitude as  $C_{\text{Alq}_3} \cdot U$  (a few  $10^{-9}$  As). Both results indicate that  $t_d$  reflects the time needed to accumulate a space-charge layer at the internal interface rather than the transit time of charge carriers. Taking into account that holes are the majority carriers in our multilayer OLED and  $j$  is proportional to  $1/t_d$ , we conclude that holes are responsible for the charge-carrier accumulation at the NPB/Alq<sub>3</sub> interface. A further argument against attributing  $t_d$  for applied voltage pulses  $\leq 9$  V to a carrier-transit time is the relatively large variation of  $t_d$  upon varying the height of the applied voltage pulse and the lack of a saturation behavior of  $t_d$  within this electric field regime (Fig. 3). Comparable results have been reported previously for a polymeric double-layer LED [31]. More comprehensive studies of EL transients from the above-mentioned multilayer OLED at lower electrical fields can be found in reference [52].

The same relationship between  $t_d$  and  $j$  is obtained for the high electrical field range, but  $t_d$  tends to saturate with increasing  $j$ , and  $j t_d$  is no longer of the same order of magnitude as  $C_{\text{Alq}_3} \cdot U$ . Again this proves that accumulated charges (holes) at the NPB/Alq<sub>3</sub> interface play a minor role at higher fields—although they are present—and that  $t_d$  is predominated by the charge-carrier transport. Such a saturation of  $t_d$  is also observed with different dc bias voltages, where  $t_d$  shows a tendency to reach a constant value as the offset voltage increases.

By the way, the peaks in the cell-current signal at the beginning and end of the applied voltage pulse (Fig. 2) are caused by the charging and discharging of the OLED, which can be treated as a capacitor, and the rise time  $t_r$  determined by the intercept of the tangents (Fig. 2) reflects saturation of the electron-carrier density in the recombination zone, i.e. at the NPB/Alq<sub>3</sub> interfacial layer.

Next we shall calculate the electron mobility in Alq<sub>3</sub> via  $t_d$  from the multilayer OLED (Fig. 3). Usually the charge-carrier mobility  $\mu$  is given by  $\mu = L/(t_{\text{tr}} F)$  with  $F = (U - U_{\text{bi}})/d$ , where  $F$  is the electric field,  $L$  the thickness of the active material,  $U$  the voltage applied to the device, and  $U_{\text{bi}}$  the built-in voltage calculated from the difference in the work functions of ITO and Mg:Ag alloy ( $U_{\text{bi}} \cong 1.2$  V). Before going into more detail we have to point out that by using  $t_d$  instead of  $t_{\text{tr}}$  (transit time obtained via TOF measurements) in the above-mentioned equation we can only obtain *apparent* values for the charge-carrier mobilities because  $t_d$  is determined by

the buildup of space charges inside the devices, and/or the charge-carrier transport behavior, dependent on the electric field range investigated. The accumulation of holes at the NPB/Alq<sub>3</sub> interface in the multilayer device as discussed above leads to a redistribution of the electric field inside the device in such a manner that the field in the electron transport layer (Alq<sub>3</sub>) increases and the field in the hole transport layer (NPB) decreases. Therefore the actual electrical-field distribution in our multilayer OLED is unknown and one can only determine upper and lower bounds of the *apparent*, only operationally defined electron mobility  $\mu_e$  in Alq<sub>3</sub> calculated from  $t_d$  for the limiting cases that (a) there exists a homogeneous electrical field within the complete device structure or (b) the entire electrical field drops across the Alq<sub>3</sub> layer. Under these assumptions,  $\mu_e$  in Alq<sub>3</sub> is between  $1.2\text{-}1.9 \times 10^{-5}$  cm<sup>2</sup>/Vs (case a) and  $2.3\text{-}3.5 \times 10^{-6}$  cm<sup>2</sup>/Vs (case b) for electric fields ranging between  $4.2 \times 10^5$  and  $3.0 \times 10^6$  V/cm (Fig. 9). In Fig. 10 we compare these calculated *apparent*  $\mu_e$  values with those published in the literature. Hosokawa et al. [12] and Kalinowski et al. [18] presented data from an ITO / N,N'-diphenyl-N,N'-bis(3-methylphenyl)-(1,1'-biphenyl)-4,4'-diamine (TPD) (60 nm) / Alq<sub>3</sub> (60 nm) / Mg:Ag double layer OLED. They have performed transient EL measurements and calculated indirect values for  $\mu_e$  in Alq<sub>3</sub> via  $t_d$  under the simplified assumption that there exists a homogeneous electric-field distribution (corresponding to our case a) inside their devices despite the presence of the TPD/Alq<sub>3</sub> interfacial layer. As shown in Fig. 10 the calculated electron mobilities of both groups are field independent in the high field range. Whereas the data of Kalinowski et al. [18] could be treated as a continuation of our results, those of Hosokawa et al. [12] differ only by a factor of 2 to 3. However, in both studies  $U_{bi}$  was not considered. Mückl et al. [22] investigated the low field range of the above-mentioned bilayer structure with the same active layer thicknesses but with a calcium cathode. For the calculation of  $\mu_e$  they considered the built-in field ( $U_{bi}$ ) of their device and assumed a drop of the entire electrical field across the Alq<sub>3</sub> layer (corresponding to our case b). They end up with a field dependence of  $\mu_e$  in the low field regime that correlates with our results. However, the data presented by Nakamura et al. [7] from an ITO / 4,4',4'',tris(N-(m-tryl)-N-phenyl-amino)-triphenylamine (MTDATA) (60 nm) / TPD (20 nm) / Alq<sub>3</sub> (60 nm) / Mg:Ag OLED are in contrast to our and all other published  $\mu_e$  values. They assume a uniformly applied electric field over the entire device (our case a) and observed a pronounced field dependence of  $\mu_e$  both in the low and high electric-field regime. The built-in voltage is not taken into consideration in their calculations.

To investigate the mechanism that determines the time evolution of EL in single-layer OLEDs we have performed transient EL measurements with an ITO / Alq<sub>3</sub> (100 nm) / Mg:Ag structure as shown in Figs. 4(b) and 5. At first sight it is striking that  $t_d$  and  $t_r$  exceed the values measured for the multilayer device. This shorter response time of the latter can be attributed to an improved injection efficiency due to the lowering of the injection barrier by inserting a thin CuPc layer between ITO and NPB [50]. A detailed study of the influence of such an interface grading in the multilayer device used in this work can be found in Ref. [53]. In addition one has to keep in mind that in the multilayer OLED the accumulation of holes [ $\mu_h$  (NPB)  $\cong 10^{-3}$  cm<sup>2</sup>/Vs [54], i.e.  $\mu_h$  (NPB)  $\gg \mu_e$  (Alq<sub>3</sub>)] at the NPB/Alq<sub>3</sub> interface enhances the electric field inside the Alq<sub>3</sub> layer and results concomitantly in an improvement of the electron injection efficiency. The recombination zone of electrons and holes in our single-layer OLED lies near the ITO anode due to the higher injection barrier for holes and their approximately two orders of magnitude lower mobility in Alq<sub>3</sub> [22, 59]. Therefore a further argument for the longer response time of the latter is the more than 60% greater Alq<sub>3</sub> layer thickness, which electrons have to cross before recombining radiatively with the first injected

holes.

In principle, in single-layer OLEDs  $t_d$  reflects the time when the two leading fronts of injected carriers—electrons and holes—meet in the sample, whereas  $t_r$  can be attributed to the time until electron and hole distributions have interpenetrated. The latter is controlled by the charge-carrier motion into the bulk of the device. An open question is which process prevails, i.e. the control of  $t_d$  by charge-carrier transport or by the accumulation of charges. Therefore the calculated values of the *apparent* electron mobility in the Alq<sub>3</sub> range between  $9.4 \times 10^{-6}$ - $1.1 \times 10^{-5}$  cm<sup>2</sup>/Vs assuming  $\mu_e \gg \mu_h$  and  $4.7$ - $5.3 \times 10^{-6}$  cm<sup>2</sup>/Vs assuming  $\mu_e = \mu_h$  at electric fields varying between  $6.8 \times 10^5$  and  $1.5 \times 10^6$  V/cm (Fig. 9). An answer to that question is provided by transient EL measurements in the single-layer device upon applying different positive or negative offset voltages before the rectangular voltage pulse (Fig. 6). With increasing negative offset voltage  $t_d$  increases and with increasing positive offset voltage  $t_d$  decreases. These results indicate that even without an apparent internal organic-organic interface  $t_d$  is determined by the accumulation of space charges and the concomitant redistribution of the electric field inside the device rather than by charge-carrier transport. Otherwise  $t_d$  should not vary with dc bias voltages. A more precise look at the EL decay behavior (inset of Fig. 6) indicates a slow decrease of the EL decay with increasing the offset voltage, which clearly proves a charging of our device by the various applied dc bias voltages.

Another argument against attributing  $t_d$  purely to transit time can be put forward by investigating the EL decay from a single-layer OLED after the voltage pulse is turned off (Fig. 7). The EL decay signal is nonexponential and can be described as the sum of two exponential decays. The first one with time constant  $\tau_A \cong 0.3 \mu\text{s}$  is determined mainly by the RC time of the experimental setup (defined as 63% of the total value), whereas the second one with time constant  $\tau_B \cong 10 \mu\text{s}$  clearly testifies to the existence of a delayed EL, which is caused by the accumulation of charge carriers.

The presence of those accumulated charges in our single-layer device is manifested also in the cell current at the end of the applied voltage pulse [Fig. 4(b)]. It takes more than  $5 \mu\text{s}$  to discharge the device, compared to  $\cong 1.5 \mu\text{s}$  required to reach equilibrium current after the voltage pulse is turned on. Till now we can only speculate where the charge-carrier accumulation takes place in the single-layer OLED. Possibly an interfacial layer is built up at the Mg:Ag cathode due to oxide formation, as previously reported from an ITO / poly(phenylphenylenevinylene) (PPPV) / Al device [26]. As our device fabrication was performed at pressures between  $4 \times 10^{-7}$  and  $2 \times 10^{-6}$  mbar rather than in ultrahigh vacuum (UHV) we cannot completely rule out that there are impurities in our OLEDs, e.g. oxygen, which can result in the buildup of such a thin interfacial layer between Alq<sub>3</sub> and Mg:Ag. Furthermore it has been shown both experimentally and theoretically in different Alq<sub>3</sub>-metal systems [55, 56, 57] that metals such as calcium, magnesium, and gold react with the Alq<sub>3</sub> to form an interfacial layer.

However, after the rectangular voltage pulse is turned off, the electrons have to pass through nearly the entire Alq<sub>3</sub> layer (100 nm) under a built-in potential of  $\cong 1.2$  V to leave the device at the cathode. On their way back to the Mg:Ag electrode the electrons may recombine radiatively with holes, which penetrated more deeply into the Alq<sub>3</sub> layer during the preceding voltage pulse on-phase, resulting in a delayed EL signal. Simulations by B. Ruhstaller [58] prove the existence of such a hole interpenetration inside the Alq<sub>3</sub> layer.

So far we have approached the goal to obtain a value for the electron mobility in Alq<sub>3</sub> in an indirect way. Exact mobility determinations hence require TOF studies. Charge-carrier transport in amorphous organic solids has been studied extensively in the past two decades [48] due to the use of these materials as photoreceptors in xerographic applications. Even the



transport in Alq<sub>3</sub> has been investigated by TOF measurements [59, 60, 61]. However, only little information exists concerning TOF studies under operation conditions of OLEDs, i.e. in typically 100-nm-thick devices, and at electric fields  $\geq 10^6$  V/cm. Further it is illegitimate to infer from the results obtained with thick ( $\mu\text{m}$ ) to thin ( $\cong 100$  nm) devices because the morphology of thin and thick films can vary and the transport in thin layers is expected to be dispersive because the carrier thermal equilibration time within the density of states (DOS) is longer than the transit time. A typical dispersive TOF signal obtained from an ITO / Alq<sub>3</sub> (150 nm) / rubrene (10 nm) / Mg:Ag device is shown in Fig. 8. A thin rubrene layer was used as CGL to ensure that a thin charge-carrier packet is generated and subsequently injected into the Alq<sub>3</sub> film. In the case of dispersive transport,  $t_{\text{tr}}$  is normally defined by the intersection of asymptotes to the plateau and trailing edge of the current transient in a double logarithmic representation as shown in Fig. 8(b). This analysis differs from those used in most theories of charge transport [48]. In theories the transit time is defined as the average arrival time ( $t_{1/2}$ ), which is the time required for the current to decrease to one-half of its value at the transit time (see also Fig. 8(b)). Transit times calculated in this manner are typically two to three times those determined by the intersection of asymptotes. However, in our case of dispersive TOF transients the mobility determination via  $t_{1/2}$  is the more appropriate method, because  $t_{1/2}$  is not characterized by the fastest charge carriers, as  $t_{\text{tr}}$  is, and therefore we end up with more realistic (averaged) values for  $\mu_e$ . The field dependence of  $\mu_e$  calculated via  $t_{1/2}$  is weak and the absolute mobility values are comparable within a factor of 2 to those obtained via transient EL measurements. Figure 9 presents this comparison of TOF and transient EL data. A more precise look at the TOF results indicates that the field dependence of  $\mu_e$  is similar to that of the multilayer OLED (transient EL studies, assuming a homogeneous electrical field within the entire device structure), whereas the absolute  $\mu_e$  values are lower. In the  $\mu_e$  calculations via  $t_d$  (transient EL data) one has to consider both the electric field and the “Schubweg” between cathode and recombination zone. The latter can be less than the Alq<sub>3</sub> layer thickness and therefore the resulting  $\mu_e$  values are higher than those determined via TOF measurements. Furthermore the absolute  $\mu_e$  values (TOF data) are higher than those obtained from the single-layer structure (transient EL studies). These are further convincing arguments that charge-carrier accumulation has an influence on  $t_d$  in the single-layer OLED. A comparison of our TOF data with literature results [59, 60, 61] is presented in Fig. 10. All published electron mobility values in Alq<sub>3</sub> obtained via TOF measurements show a pronounced electric-field dependence. In addition these mobilities vary over several orders of magnitude. None of these effects were observed in our studies. These discrepancies from our work and among the literature data themselves might be attributed to deviations in the layer thickness of the films investigated, as pointed out above. To the best of our knowledge the TOF investigations presented in this work are the first to have been performed with only 150-nm-thick Alq<sub>3</sub> films, i.e. a film thickness commonly used in OLED devices. By the way the portrayed literature data (Fig. 10) were calculated via  $t_{\text{tr}}$  and not via  $t_{1/2}$ . Furthermore the deposition rate has a distinct influence on  $\mu_e$ . It was recently found that the electron mobility in Alq<sub>3</sub> increases by about two orders of magnitude as the deposition rate decreases from 0.7 to 0.2 nm/s [62], whereas we used a deposition rate of 0.1 nm/s.

## 5 Conclusions

We have presented transient EL measurements from ITO / CuPc (20 nm) / NPB (45 nm) / Alq<sub>3</sub> (50 nm) / Mg:Ag multilayer and ITO / Alq<sub>3</sub> (100 nm) / Mg:Ag single-layer OLEDs. In the multilayer device the EL onset is limited by accumulated charges (holes) at the internal organic-organic interface (NPB/Alq<sub>3</sub>) for  $E \leq 7.7 \times 10^5$  V/cm (case a) and  $E \leq 1.8 \times 10^6$  V/cm (case b) and transport limited in the high-electric-field range [ $E \geq 8.5 \times 10^5$  V/cm (case a) and  $E \geq 2.0 \times 10^6$  V/cm (case b)]. For the single-layer system, experiments with various offset voltages and analysis of the EL decay behavior manifest that  $t_d$  is determined by the accumulation of charge carriers rather than by charge-carrier transport. Therefore the determination of  $\mu_e$  in Alq<sub>3</sub> is possible only for various limiting cases and must be considered a rough approximation. More accurate  $\mu_e$  values are obtained from TOF measurements, which were performed for the first time on only 150-nm-thick Alq<sub>3</sub> layers and electric fields of up to  $1.3 \times 10^6$  V/cm. Furthermore we proved that insertion of a thin CuPc buffer layer between ITO and NPB, the use of separate improved layers for electron and hole transport and/or driving the devices with positive offset voltages yield a faster EL onset and rise, which are crucial parameters for the application of OLEDs in flat-panel displays.

## Acknowledgment

The authors are indebted to H. Schmid for his assistance in realizing a computer-controlled experimental setup and M. Tschudy for his support with the device fabrication. We thank B. Ruhstaller for helpful discussions. This work is supported by the Fond der Chemischen Industrie.

## References

- [1] C. W. Tang and S. A. Van Slyke, *Appl. Phys. Lett.* **51**, 913 (1987).
- [2] C. W. Tang, S. A. Van Slyke, and C. H. Chen, *J. Appl. Phys.* **65**, 3610 (1989).
- [3] C. Adachi, T. Tsutsui, and S. Saito, *Appl. Phys. Lett.* **56**, 799 (1990).
- [4] J. Kido, M. Kimura, and K. Nagai, *Science* **267**, 1322 (1995).
- [5] T. Wakimoto, R. Murayama, K. Nagayama, Y. Okuda, H. Nakada, and T. Tohma, *Proc. SID '96 Int'l Symp., Digest of Technical Papers, San Diego (1996)* p. 849.
- [6] H. Nakada and T. Tohma, *Proc. Int'l Symp. on Inorganic and Organic Electroluminescence*, edited by R. H. Mauch and H. -E. Gumlich (Wissenschaft und Technik Verlag, Berlin, 1996) 385.
- [7] H. Nakamura, C. Hosokawa, and T. Kusumoto, *Proc. Int'l Symp. on Inorganic and Organic Electroluminescence*, edited by R. H. Mauch and H. -E. Gumlich (Wissenschaft und Technik Verlag, Berlin, 1996) 95.
- [8] Y. Hamada, T. Sano, H. Fujii, Y. Nishio, H. Takahashi, and K. Skibata, *Jpn. J. Appl. Phys.* **35**, 1339 (1996).

- [9] For recent progress see: *Organic Electroluminescent Materials and Devices*, edited by S. Miyata and H. S. Nalwa (Gordon and Breach, Lausanne, 1997).
- [10] W. Helfrich and W. G. Schneider, *Phys. Rev. Lett.* **14**, 229 (1965).
- [11] D. F. Williams and M. Schadt, *J. Chem. Phys.* **53**, 3480 (1970).
- [12] C. Hosokawa, H. Tokailin, H. Higashi, and T. Kusumoto, *Appl. Phys. Lett.* **60**, 1220 (1992).
- [13] Y. Ohmori, C. Morishima, M. Uchida, and K. Yoshino, *Jpn. J. Appl. Phys.* **31**, L568 (1992).
- [14] C. Hosokawa, H. Tokailin, H. Higashi, and T. Kusumoto, *Appl. Phys. Lett.* **63**, 1322 (1993).
- [15] P. Delannoy, G. Horowitz, H. Bouchriha, F. Deloffre, J. -L. Fave, F. Garnier, R. Hajlaoui, M. Heyman, F. Kouki, J. -L. Monge, P. Valat, V. Wintgens, and A. Yassar, *Synth. Met.* **67**, 197 (1994).
- [16] A. J. Pal, R. Österbacka, K. -M. Källman, and H. Stubb, *Appl. Phys. Lett.* **71**, 228 (1997).
- [17] P. Ranke, I. Bleyl, J. Simmerer, D. Haarer, A. Bacher, H. W. Schmidt, *Appl. Phys. Lett.* **71**, 1332 (1997).
- [18] J. Kalinowski, N. Camaioni, P. Di Marco, V. Fattori, and A. Martelli, *Appl. Phys. Lett.* **72**, 513 (1998).
- [19] G. Kranzelbinder, F. Meghdadi, S. Tasch, G. Leising, L. Fasoli, M. Sampietro, *Synth. Met.* **102**, 1073 (1999).
- [20] Y. Ohmori, N. Tada, Y. Kurosaka, and K. Yoshino, *Synth. Met.* **102**, 1099 (1999).
- [21] A. Chowdhury, A. J. Pal, *Synth. Met.* **106**, 85 (1999).
- [22] A. G. Mückl, S. Berleb, W. Brütting, and M. Schwoerer, *Synth. Met.*, Proc. 2nd Int'l Conf. on Electroluminescence of Molecular Materials and Related Phenomena (ICEL 2), Sheffield, UK, May 13-15, 1999 (in press).
- [23] K. Book, H. Bässler, V. R. Nikitenko, A. Elschner, *Synth. Met.*, Proc. 2nd Int'l Conf. on Electroluminescence of Molecular Materials and Related Phenomena (ICEL 2), Sheffield, UK, May 13-15, 1999 (in press).
- [24] D. Braun, D. Moses, C. Zhang, and A. J. Heeger, *Appl. Phys. Lett.* **61**, 3092 (1992).
- [25] D. Braun, D. Moses, C. Zhang, and A. J. Heeger, *Synth. Met.* **55-57**, 4145 (1993).
- [26] H. Vestweber, J. Oberski, A. Greiner, W. Heitz, R. F. Mahrt, and H. Bässler, *Adv. Mater. Opt. Electron.* **2**, 197 (1993).
- [27] H. Vestweber, R. Sander, A. Greiner, W. Heitz, R. F. Mahrt, and H. Bässler, *Synth. Met.* **64**, 141 (1994).

- [28] S. Karg, V. Dyakonov, M. Meier, W. Rieß, and G. Paasch, *Synth. Met.* **67**, 165 (1994).
- [29] S. Kirstein, G. Cohen, D. Davidov, U. Scherf, M. Klapper, K. Chmil, and K. Müllen, *Synth. Met.* **69**, 415 (1995).
- [30] Y. -H. Tak, H. Vestweber, H. Bässler, A. Bleyer, R. Stockmann, H. -H. Hörhold, *Chem. Phys.* **212**, 471 (1996).
- [31] J. Pommerehne, H. Vestweber, Y. -H. Tak, and H. Bässler, *Synth. Met.* **76**, 67 (1996).
- [32] D. R. Baigent, P. G. May, R. H. Friend, *Synth. Met.* **76**, 149 (1996).
- [33] Y. -H. Tak, J. Pommerehne, H. Vestweber, R. Sander, H. Bässler, H. -H. Hörhold, *Appl. Phys. Lett.* **69**, 1291 (1996).
- [34] H. Chayet, R. Pogreb, and D. Davidov, *Phys. Rev. B* **56**, R12702 (1997).
- [35] T. Östergard, A. J. Pal, and H. Stubb, *J. Appl. Phys.* **83**, 2338 (1998).
- [36] R. Österbacka, G. Juška, K. Arlauskas, A. J. Pal, K. -M. Källman, and H. Stubb, *J. Appl. Phys.* **84**, 3359 (1998).
- [37] P. W. M. Blom and M. C. J. M. Vissenberg, *Phys. Rev. Lett.* **80**, 3819 (1998).
- [38] A. J. Pal, T. Östergard, R. Österbacka, J. Puloheimo, and H. Stubb, *IEEE J. Sel. Top. Quantum Electron.* **4**, 137 (1998).
- [39] N. Tessler, N. T. Harrison, D. S. Thomas, and R. H. Friend, *Appl. Phys. Lett.* **73**, 732 (1998).
- [40] N. Tessler, N. T. Harrison, and R. H. Friend, *Adv. Mater.* **10**, 64 (1998).
- [41] V. Savvateev, A. Yakimov, and D. Davidov, *Adv. Mater.* **11**, 519 (1999).
- [42] M. C. J. M. Vissenberg, P. W. M. Blom, *Synth. Met.* **102**, 1053 (1999).
- [43] D. J. Pinner, N. Tessler, R. H. Friend, *Synth. Met.* **102**, 1108 (1999).
- [44] D. J. Pinner, R. H. Friend, N. Tessler, *J. Appl. Phys.* **86**, 5116 (1999).
- [45] D. J. Pinner, R. H. Friend, N. Tessler, *Synth. Met., Proc. 2nd Int'l Conf. on Electroluminescence of Molecular Materials and Related Phenomena (ICEL 2)*, Sheffield, UK, May 13-15, 1999 (in press).
- [46] V. R. Nikitenko, V. I. Arkhipov, Y. -H. Tak, J. Pommerehne, H. Bässler, H. -H. Hörhold, *J. Appl. Phys.* **81**, 7514 (1997).
- [47] V. R. Nikitenko, Y. -H. Tak, and H. Bässler, *J. Appl. Phys.* **84**, 2334 (1998).
- [48] P. M. Borsenberger, D. S. Weiss, *Organic Photoreceptors for Imaging Systems*, (Marcel Dekker, New York, 1992).
- [49] C. Hosokawa, H. Higashi, H. Nakamura, and T. Kusumoto, *Appl. Phys. Lett.* **67**, 3853 (1995).

- [50] S. A. VanSlyke, C. H. Chen, and C. W. Tang, *Appl. Phys. Lett.* **69**, 2160 (1996).
- [51] H. Vestweber and W. Rieß, *Synth. Met.* **91**, 181 (1997).
- [52] W. Brütting, H. Riel, T. Beierlein, and W. Rieß, to be published.
- [53] H. Riel, W. Brütting, T. Beierlein, E. Haskal, P. Müller, and W. Rieß, *Synth. Met.*, Proc. 2nd Int'l Conf. on Electroluminescence of Molecular Materials and Related Phenomena (ICEL 2), Sheffield, UK, May 13-15, 1999 (in press).
- [54] C. W. Tang, private communication.
- [55] S. T. Lee, X. Y. Hou, M. G. Mason, C. W. Tang, *Appl. Phys. Lett.* **72**, 1593 (1998).
- [56] V. -E. Choong, M. G. Mason, C. W. Tang, Y. Gao, *Appl. Phys. Lett.* **72**, 2689 (1998).
- [57] A. Curioni and W. Andreoni, *Synth. Met.*, Proc. 2nd Int'l Conf. on Electroluminescence of Molecular Materials and Related Phenomena (ICEL 2), Sheffield, UK, May 13-15, 1999 (in press).
- [58] B. Ruhstaller, to be published.
- [59] R. G. Kepler, P. M. Beeson, S. J. Jacobs, R. A. Anderson, M. B. Sinclair, V. S. Valencia, and P. A. Cahill, *Appl. Phys. Lett.* **66**, 3618 (1995).
- [60] B. Chen and S. Liu, *Synth. Met.* **91**, 169 (1997).
- [61] T. Tsutsui, H. Tokuhisa, M. Era, Proc. SPIE Vol. 3281, *Polymer Photonic Devices*, edited by B. Kippelen and D. D. C. Bradley, 230-239, 1998.
- [62] B. J. Chen, W. Y. Lai, Z. Q. Gao, C. S. Lee, S. T. Lee, and W. A. Gambling, *Appl. Phys. Lett.* **75**, 4010 (1999).

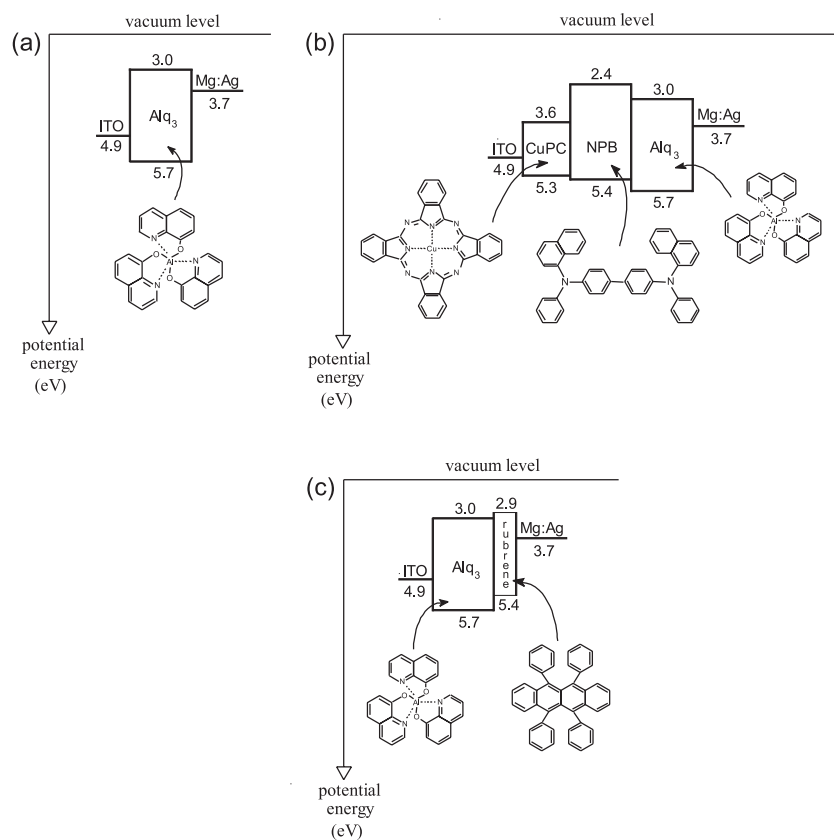


Figure 1: Schematic energy-level diagram, device structure, and molecular structure of the investigated (a) single-layer OLED, (b) multilayer OLED, and (c) sample used for TOF measurements.

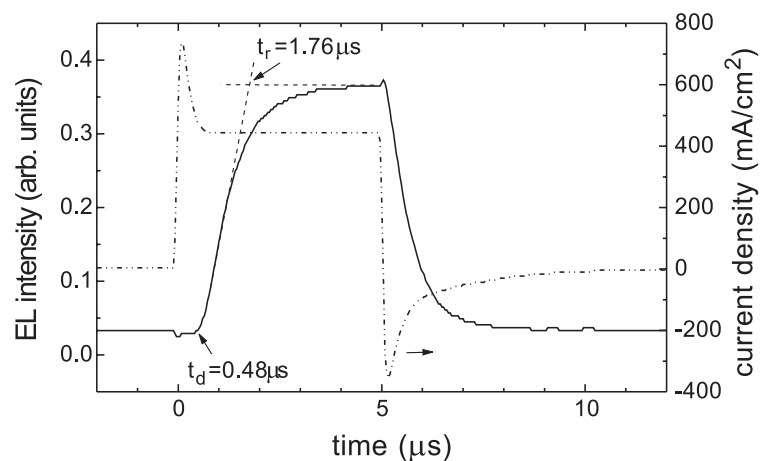


Figure 2: Comparison between time response of EL and cell current in an ITO / CuPc (20 nm) / NPB (45 nm) / Alq<sub>3</sub> (50 nm) / Mg:Ag multilayer OLED upon application of a rectangular voltage pulse of 16 V with a pulse length of 5  $\mu$ s and a repetition rate of 1 kHz. The EL signal was averaged over 256 samples.

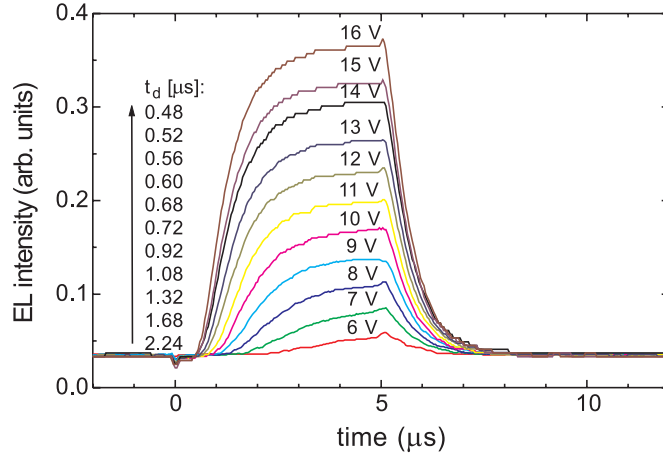


Figure 3: Voltage dependence of the transient EL from an ITO / CuPc (20 nm) / NPB (45 nm) / Alq<sub>3</sub> (50 nm) / Mg:Ag multilayer OLED. The pulse width was 5  $\mu$ s and the repetition rate 1 kHz.

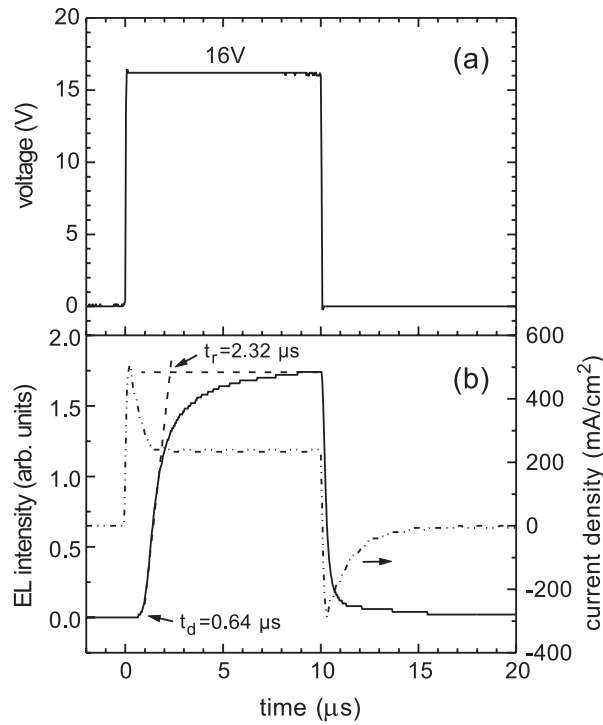


Figure 4: (a) Typical function generator output signal of 10 s pulse length. (b) Comparison between transient EL and cell current in an ITO / Alq<sub>3</sub> (100 nm) / Mg:Ag single-layer OLED upon application of a rectangular voltage pulse of 16 V. The pulse length was 10  $\mu$ s, the repetition rate 1 kHz, and the EL was averaged over 256 samples.

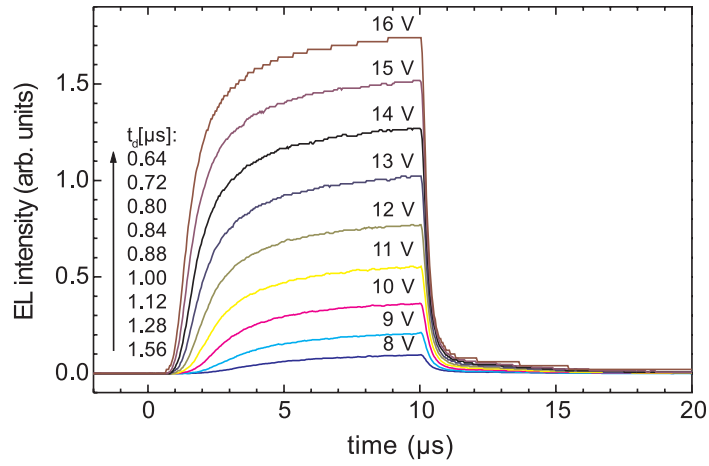


Figure 5: Voltage dependence of the time-resolved EL from an ITO / Alq<sub>3</sub> (100 nm) / Mg:Ag single-layer device. The pulse length was 10  $\mu$ s and the repetition rate 1 kHz.

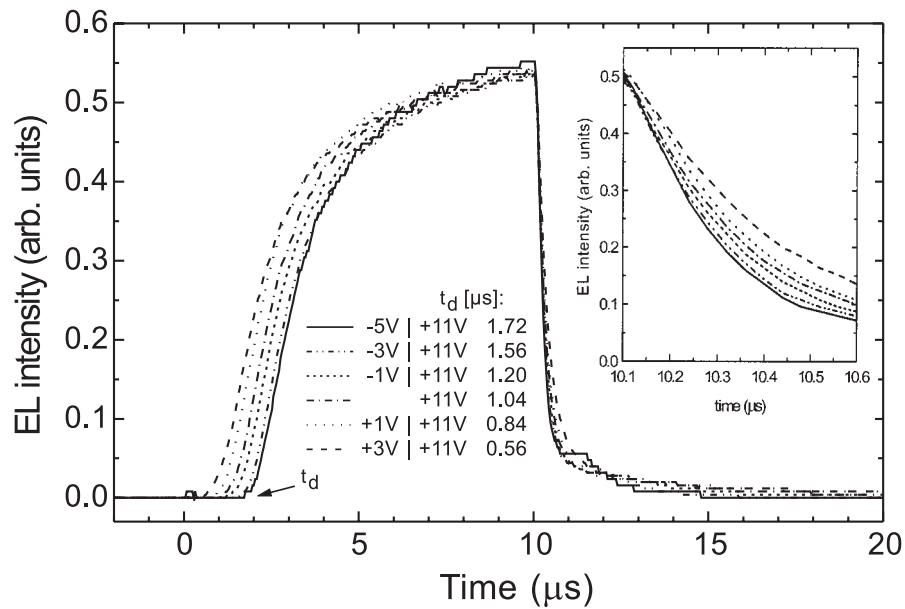


Figure 6: Comparison of the time response of EL from an ITO / Alq<sub>3</sub> (100 nm) / Mg:Ag OLED upon application of various offset voltages before a 10- $\mu$ s-long rectangular pulse was applied with a repetition rate of 1 kHz. Inset: enlargement of the EL decay signals for the various applied offset voltages.



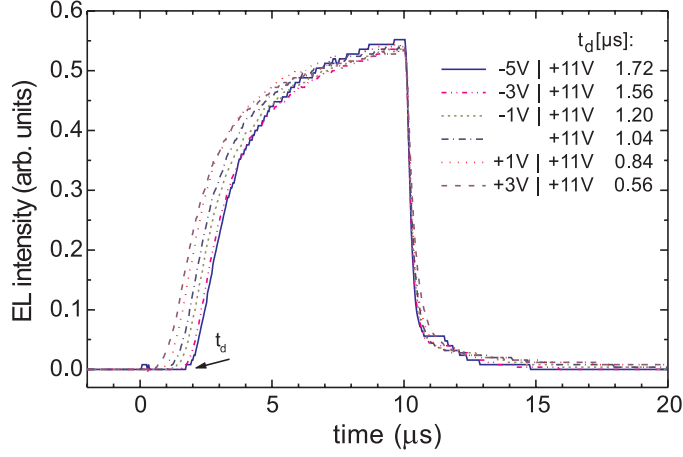


Figure 7: EL decay behavior at the falling edge of a 10- $\mu$ s-long rectangular 8 V pulse from an ITO / Alq<sub>3</sub> (100 nm) / Mg:Ag single-layer structure on a semilogarithmic scale. The EL decay is nonexponential and can be described as the sum of two exponential decays with time constants of  $\tau_A \cong 0.3 \mu$ s and  $\tau_B \cong 10 \mu$ s.

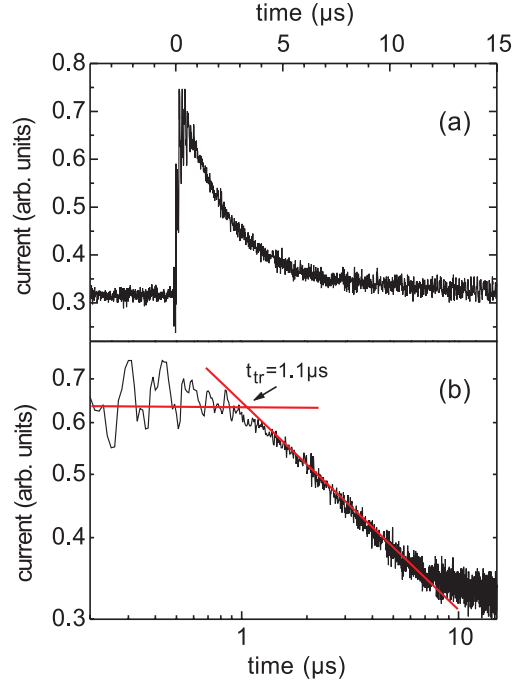


Figure 8: Typical current transient from an ITO / Alq<sub>3</sub> (150 nm) / rubrene (10 nm) / Mg:Ag device in (a) a double linear and (b) double logarithmic representation at  $E = 5.9 \times 10^5$  V/cm. The excitation was through the positively biased ITO electrode at  $\lambda_{\text{exc}} = 530$  nm. Via the intersection of the asymptotes with the plateau and trailing edge of the current transient,  $t_{\text{tr}}$  is determined to be 1.1  $\mu$ s. Additionally marked is the time required for the current to decrease to one-half of its value at  $t_{\text{tr}}$  ( $t_{1/2} = 2.4 \mu$ s);  $\mu_e = 2.3 \times 10^{-5}$  cm<sup>2</sup>/Vs (via  $t_{\text{tr}}$ ) and  $\mu_e = 1.1 \times 10^{-5}$  cm<sup>2</sup>/Vs (via  $t_{1/2}$ ).

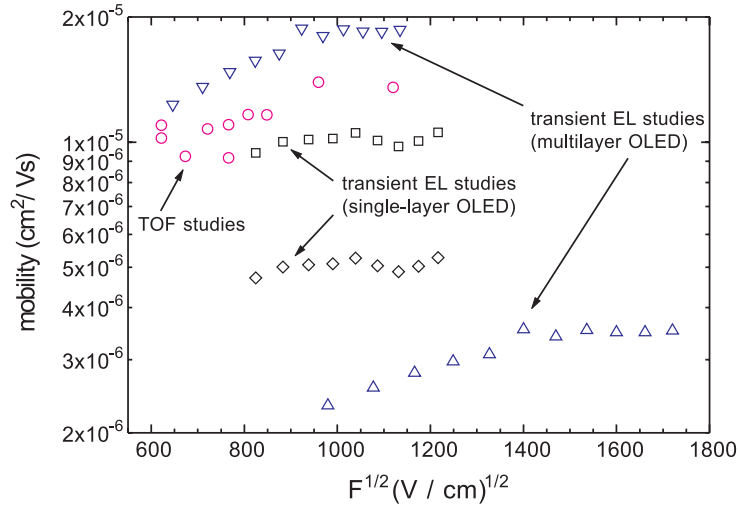


Figure 9: Electric-field dependence for upper and lower bounds of the apparent electron mobility in  $\text{Alq}_3$  calculated via  $t_d$  from time-resolved EL measurements: for the ITO / CuPc (20 nm) / NPB (45 nm) /  $\text{Alq}_3$  (50 nm) / Mg:Ag multilayer OLED assuming that one of the following limiting cases occurs: (a) there exists a homogeneous electrical field within the complete device structure (down triangles) or (b) the entire electric field drops across the  $\text{Alq}_3$  layer (up triangles). For the ITO /  $\text{Alq}_3$  (100 nm) / Mg:Ag single-layer OLED under the assumptions: (a)  $\mu_e \gg \mu_h$  (squares) and (b)  $\mu_e = \mu_h$  (diamonds). For comparison  $\mu_e$  values from TOF measurements of an ITO /  $\text{Alq}_3$  (150 nm) / rubrene (10 nm) / Mg:Ag device calculated via  $t_{1/2}$  are presented (circles).  $U_{\text{bi}} = 1.2$  V was considered for all calculations, i.e. transient EL and TOF.

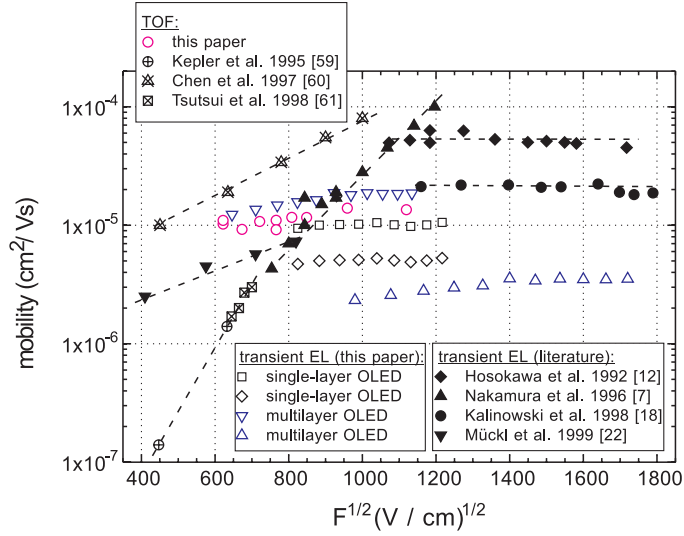


Figure 10: Comparison of the electric-field dependence of  $\mu_e$  in Alq<sub>3</sub> calculated in this paper via time-resolved EL and TOF studies (see Fig. 9) with data published in the literature. The latter were obtained via transient EL measurements from the following device structures: ITO / TPD (60 nm) / Alq<sub>3</sub> (60 nm) / Mg:Ag (Hosokawa et al. [12] and Kalinowski et al. [18]), ITO / TPD (60 nm) / Alq<sub>3</sub> (60 nm) / Ca (Mückl et al. [22]), ITO / MTDATA (60 nm) / TPD (20nm) / Alq<sub>3</sub> (60 nm) / Mg:Ag (Nakamura et al. [7]). The TOF studies were performed with the following device structures: Si / Alq<sub>3</sub> (400 nm) / Al (Kepler et al. [59]) and Si / Alq<sub>3</sub> (200 nm) / Au (Chen et al. [59]). A description of the sample structure used by Tsutsui et al. [61] is missing in their paper.